
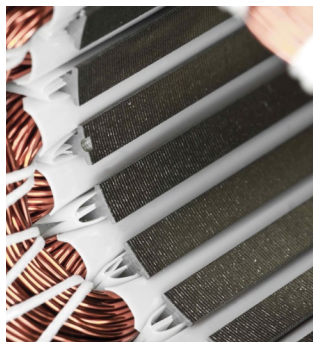


# DI-MAX<sup>®</sup> HF-12

## COLD ROLLED FULLY PROCESSED NON-ORIENTED ELECTRICAL STEEL

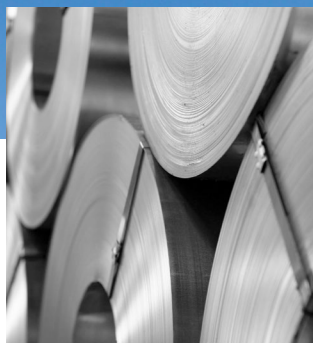

**Aircraft Generators**

**High Speed Motors**

**Traction Motors**



**DI-MAX<sup>®</sup> HF-12** is a fully processed non-oriented electrical steel designed for use in high speed motors, traction motors, aircraft generators, and other rotating equipment operating at frequencies above 60 Hz. DI-MAX HF-12 electrical steel is supplied in a nominal thickness of 0.30 mm.

## Product Description

Composition		(wt %)
Silicon	(Si)	3.1
Aluminum	(Al)	0.8

### MAGNETIC PROPERTIES

Release grading is based on as-sheared Epstein test and based on core loss at 1.0 T and 400 Hz in accordance with ASTM A343 (reference data at frequencies above 400 Hz were developed in conformance with ASTM A348). Representative properties using stress relief annealing are shown for reference.

### CORE LOSS

	Typical	Maximum
As-Sheared	13.8 W/kg	16.0 W/kg
After 830 °C SRA	12.5 W/kg	15.0 W/kg

### OTHER MAGNETIC PROPERTIES

Magnetic Induction at 2500 A/m (B25)	1.55 T
Magnetic Induction at 5000 A/m (B50)	1.64 T
Volume Resistivity	56 μΩ•cm
Saturation Induction	1.98 T

### INSULATIVE COATING

	C-5 Phosphate	CARLITE® 3 ANTI-STICK™
Type	ASTM A976 C-5	ASTM A976 C-5-AS
Components	Inorganic with some organic material	Inorganic
Thickness	2.3 – 2.8 μm	0.25 – 0.76 μm
Space Factor	96.6% @ 1.0 MPa 96.4% @ 0.345 MPa	97.6% @ 1.0 MPa 97.4% @ 0.345 MPa
Franklin Current	0.02 A	0.3 – 0.9 A
Weldability	Good (minimal porosity)	Excellent (no porosity)

### MECHANICAL AND PHYSICAL PROPERTIES

Density	≤ 7.65 gm/cm <sup>3</sup>
Yield Strength	400 MPa
Tensile Strength	500 MPa
Elongation, % in 2"	20%
Rockwell Hardness	B90
Vickers Hardness	193
Thickness Aim	0.30 mm
Tolerance	±0.02 mm
Strip Crown	0.005 – 0.006 mm

All values typical unless otherwise noted.



## Core Loss And Exciting Power Tables As Sheared

B (T)	H (A/m)	CORE LOSS (W/kg) @ Frequency (Hz)											
		50	60	100	200	300	400	800	1000	2000	2500	5000	10000
0.2	27.0	0.0508	0.0626	0.116	0.282	0.491	0.741	2.10	2.97	8.91	12.7	38.3	117
0.3	32.2	0.108	0.134	0.248	0.606	1.050	1.580	4.43	6.22	18.4	26.0	76.7	239
0.4	36.8	0.179	0.222	0.414	1.020	1.780	2.67	7.51	10.5	30.6	43.4	129	–
0.5	41.4	0.261	0.324	0.607	1.510	2.64	3.98	11.2	15.7	45.8	65.0	196	–
0.6	46.5	0.352	0.438	0.826	2.06	3.63	5.51	15.5	21.8	64.1	91.7	–	–
0.7	52.3	0.453	0.565	1.070	2.69	4.77	7.23	20.5	28.9	–	–	–	–
0.8	59.2	0.565	0.705	1.340	3.40	6.03	9.18	26.3	37.2	–	–	–	–
0.9	68.1	0.690	0.860	1.640	4.17	7.44	11.4	32.9	46.7	–	–	–	–
1.0	79.9	0.828	1.030	1.970	5.03	9.00	13.8	40.4	57.6	–	–	–	–
1.1	97.9	0.986	1.230	2.35	6.00	10.8	16.5	49.0	70.5	–	–	–	–
1.2	131	1.170	1.470	2.79	7.12	12.8	19.7	–	–	–	–	–	–
1.3	213	1.420	1.770	3.35	8.52	15.3	23.5	–	–	–	–	–	–
1.4	518	1.750	2.17	4.03	10.2	18.2	27.9	–	–	–	–	–	–
1.5	1580	2.14	2.66	5.01	12.6	22.4	34.4	–	–	–	–	–	–
1.6	3710	2.57	3.20	6.02	15.0	26.7	41.1	–	–	–	–	–	–
1.7	7040	3.12	3.90	–	–	–	–	–	–	–	–	–	–

B (T)	EXCITING POWER (VA/kg) @ Frequency (Hz)											
	50	60	100	200	300	400	800	1000	2000	2500	5000	10000
0.2	0.114	0.139	0.239	0.516	0.829	1.180	2.88	3.91	10.7	14.9	42.8	140
0.3	0.207	0.251	0.438	0.964	1.570	2.25	5.68	7.75	21.3	29.8	85.1	273
0.4	0.315	0.383	0.672	1.500	2.47	3.57	9.15	12.5	34.7	48.7	141	–
0.5	0.440	0.535	0.943	2.12	3.52	5.12	13.3	18.3	51.2	72.2	213	–
0.6	0.583	0.710	1.250	2.84	4.73	6.90	18.1	25.0	71.2	101	–	–
0.7	0.749	0.912	1.610	3.66	6.12	8.96	23.8	33.0	–	–	–	–
0.8	0.944	1.150	2.03	4.61	7.72	11.3	30.3	42.2	–	–	–	–
0.9	1.180	1.43	2.52	5.71	9.56	14.0	37.9	53.1	–	–	–	–
1.0	1.470	1.78	3.13	7.05	11.7	17.2	46.8	65.8	–	–	–	–
1.1	1.850	2.25	3.92	8.74	14.5	21.2	57.4	80.8	–	–	–	–
1.2	2.44	2.96	5.12	11.2	18.3	26.6	–	–	–	–	–	–
1.3	3.68	4.45	7.61	16.2	25.8	36.6	–	–	–	–	–	–
1.4	8.13	9.85	15.4	31.7	48.8	67.2	–	–	–	–	–	–
1.5	26.6	32.3	54.7	111	169	229	–	–	–	–	–	–
1.6	73.2	88.7	150	303	460	622	–	–	–	–	–	–
1.7	157	191	–	–	–	–	–	–	–	–	–	–

7.60 gm/cm<sup>3</sup> test density  
 ASTM A343, ASTM A348; 50/50  
 B = Magnetic induction  
 H = Applied field

## Core Loss And Exciting Power Tables Stress Relief Annealed

B (T)	H (A/m)	CORE LOSS (W/kg) @ Frequency (Hz)											
		50	60	100	200	300	400	800	1000	2000	2500	5000	10000
0.2	23.2	0.0424	0.0521	0.0958	0.234	0.409	0.620	1.790	2.55	7.73	11.3	34.1	108
0.3	27.2	0.0894	0.110	0.204	0.499	0.874	1.330	3.79	5.37	16.1	23.3	69.8	220
0.4	30.4	0.150	0.186	0.345	0.854	1.500	2.27	6.45	9.18	27.0	39.0	117	–
0.5	33.3	0.222	0.276	0.517	1.280	2.26	3.43	9.78	13.8	40.5	58.7	180	–
0.6	36.4	0.305	0.379	0.714	1.79	3.16	4.79	13.7	19.3	57.0	82.9	–	–
0.7	40.0	0.398	0.496	0.938	2.36	4.18	6.36	18.2	25.8	–	–	–	–
0.8	44.7	0.502	0.626	1.190	3.01	5.35	8.19	23.6	33.4	–	–	–	–
0.9	51.1	0.619	0.771	1.470	3.73	6.68	10.2	29.7	42.4	–	–	–	–
1.0	60.4	0.751	0.936	1.780	4.56	8.17	12.5	36.9	52.8	–	–	–	–
1.1	75.2	0.905	1.130	2.14	5.48	9.86	15.2	45.3	65.2	–	–	–	–
1.2	102	1.090	1.360	2.57	6.55	11.8	18.2	–	–	–	–	–	–
1.3	164	1.330	1.650	3.11	7.88	14.1	21.8	–	–	–	–	–	–
1.4	388	1.660	2.07	3.87	9.68	17.3	26.6	–	–	–	–	–	–
1.5	1370	2.06	2.56	4.78	11.9	21.0	32.3	–	–	–	–	–	–
1.6	3570	2.42	3.01	5.63	13.9	24.7	38.1	–	–	–	–	–	–
1.7	6980	2.85	3.58	–	–	–	–	–	–	–	–	–	–

B (T)	EXCITING POWER (VA/kg) @ Frequency (Hz)											
	50	60	100	200	300	400	800	1000	2000	2500	5000	10000
0.2	0.0964	0.117	0.200	0.429	0.685	0.970	2.40	3.28	9.04	12.9	38.1	126
0.3	0.174	0.210	0.365	0.800	1.300	1.870	4.78	6.58	18.3	26.2	76.4	254
0.4	0.261	0.317	0.555	1.240	2.05	2.98	7.76	10.7	30.1	43.1	127	–
0.5	0.359	0.438	0.775	1.760	2.93	4.29	11.4	15.7	44.5	64.1	193	–
0.6	0.470	0.574	1.020	2.34	3.94	5.80	15.6	21.7	62.1	90.1	–	–
0.7	0.596	0.729	1.300	3.01	5.10	7.54	20.5	28.7	–	–	–	–
0.8	0.743	0.909	1.630	3.78	6.43	9.55	26.2	36.9	–	–	–	–
0.9	0.919	1.120	2.01	4.68	7.97	11.9	33.0	46.6	–	–	–	–
1.0	1.140	1.390	2.49	5.76	9.80	14.6	40.9	58.2	–	–	–	–
1.1	1.440	1.760	3.12	7.14	12.1	17.9	50.5	72.2	–	–	–	–
1.2	1.90	2.32	4.07	9.12	15.2	22.4	–	–	–	–	–	–
1.3	2.83	3.44	5.94	12.8	20.8	30.1	–	–	–	–	–	–
1.4	5.97	7.27	12.3	25.5	39.5	55.0	–	–	–	–	–	–
1.5	22.2	27.3	45.7	92.9	142	193	–	–	–	–	–	–
1.6	69.2	84.1	141	286	435	588	–	–	–	–	–	–
1.7	155	188	–	–	–	–	–	–	–	–	–	–

7.60 gm/cm<sup>3</sup> test density  
 ASTM A343, ASTM A348; 50/50  
 B = Magnetic induction  
 H = Applied field



# POWERING PROGRESS

SAFETY | QUALITY | PRODUCTIVITY | INNOVATION



A CLEVELAND-CLIFFS COMPANY

AK Steel Corporation  
9227 Centre Pointe Drive  
West Chester, OH 45069  
844.STEEL99 | 844.783.3599

[www.aksteel.com](http://www.aksteel.com)  
[sales@aksteel.com](mailto:sales@aksteel.com)

Founded in 1847, Cleveland-Cliffs is among the largest vertically integrated producers of differentiated iron ore and steel in North America. With an emphasis on non-commoditized products, the Company is uniquely positioned to supply both customized iron ore pellets and steel solutions to a quality-focused customer base. AK Steel, a wholly-owned subsidiary of Cleveland-Cliffs, is a leading producer of flat-rolled carbon, stainless and electrical steel products. The AK Tube and Precision Partners businesses provide customer solutions with carbon and stainless steel tubing products, die design and tooling, and hot- and cold-stamped components. In 2020, Cliffs also expects to be the sole producer of hot briquetted iron (HBI) in the Great Lakes region. Headquartered in Cleveland, Ohio, Cleveland-Cliffs employs approximately 11,000 people across mining and steel manufacturing operations in the United States and Canada.

Additional information about AK Steel is available at [www.aksteel.com](http://www.aksteel.com).

AK and the AK Steel logo are registered trademarks of the AK Steel Corporation. ©2020 AK Steel. All Rights Reserved.

5.20